

ASBESTOS: MINERALOGY, HEALTH HAZARDS AND PUBLIC POLICY

Helen M. Lang

Department of Geology and Geography
West Virginia University
P.O. Box 6300
Morgantown, West Virginia 26506-6300
hlang@wvu.edu

Sid P. Halsor

Department of GeoEnvironmental Science & Engineering
Wilkes University
Wilkes-Barre, Pennsylvania 18766
shalsor@wilkes1.wilkes.edu

BACKGROUND

Asbestos refers to certain minerals that have a fibrous habit and are useful for their insulating, heat and chemically resistant properties. Asbestos has been used extensively for over a century in electrical and heat insulation, fireproofing materials, brake and clutch linings, construction materials, filters and many other applications. Recently, the U.S. has severely restricted the use of asbestos, and has a program for removing asbestos from schools and other public buildings (See Gunter, 1994; Ross, 1995 and references therein). In this laboratory exercise you will have an opportunity to examine the crystal structures, optical properties and health hazards of the common asbestos minerals. The laboratory will reinforce optical microscopic skills that you have learned in mineralogy and show you how mineralogy can be critical to understanding a current public policy issue.

Although mineralogists reserve the designation asbestos for fibrous material with a length:width ratio (aspect ratio) of at least 10:1 (Skinner, et al., 1988), asbestos is defined by OSHA (U.S. Occupational Safety and Health Administration, 1972; Web address is given below) as mineral material composed of any of the six silicate minerals in Table 1 with a length:width ratio of 3:1 or greater, diameter less than 5 μm and length greater than 5 μm .

Table 1. Asbestos Minerals

Mineral	Asbestos name	Mineral Group	Approx. Formula	Comments
Riebeckite		Crocidolite (blue)		clino-amphibole
	$\text{Na}_2\text{Fe}^{3+}_2(\text{Fe}^{2+}, \text{Mg})_3\text{Si}_8\text{O}_{22}(\text{OH})_2$		e.g. in pC BIF	
Grunerite	Amosite (brown)	clino-amphibole	$(\text{Fe}^{2+})_2(\text{Fe}^{2+}, \text{Mg})_5\text{Si}_8\text{O}_{22}(\text{OH})_2$	e.g. in pC BIF, Transvaal, S.A.
Anthophyllite		ortho-amphibole	$\text{Mg}_7\text{Si}_8\text{O}_{22}(\text{OH})_2$	Alpine UM rx
Actinolite	Byssolite	clino-amphibole	$\text{Ca}_2(\text{Mg}, \text{Fe}^{2+})_5\text{Si}_8\text{O}_{22}(\text{OH})_2$	e.g. East Finland
asbestiform				rarely

The octahedral sheet of serpentine filled with Mg^{2+} ($b \sim 9.36 \text{ \AA}$) is slightly larger than the tetrahedral sheet of serpentine filled with Si^{4+} ($b \sim 9.05 \text{ \AA}$). When these two mismatched sheets bond together (share oxygens), they tend to curl with the bigger octahedral sheet outside and the smaller tetrahedral sheet inside. In chrysotile, this results in tightly rolled sheets that form long, thin, flexible fibers. Only under very high magnification in the high resolution transmission electron microscope (HRTEM) can the rolled sheets be seen (Fig. 1).

Figure 1. High resolution transmission electron microscope images of chrysotile. a. Packing of chrysotile fibrils in cross-fiber chrysotile asbestos. b. Higher magnification images of chrysotile fibrils with various roll structures viewed parallel to the fibril axis (after Veblen & Wylie,

1993).

ACTIVITY 2 - MACROSCOPIC AND MICROSCOPIC PROPERTIES

"Hand" samples of each of the types of asbestos are available for you to examine. (Ward's Earth Science, Asbestos Standards Set, 49 E 5840, \$126) The samples are sealed in plastic bags so you won't breathe any fibers. Leave the bags closed and handle the samples as little as possible. Crocidolite ("blue" asbestos) is the most hazardous, and chrysotile ("white" asbestos) poses no hazard to the casual observer. At least one of the samples looks more like cleavage fragments than true asbestos, which one? Write down the properties of each of the mineral samples that you can see with the naked eye, hand lens or binocular microscope. Include approximate length and width of fibers, color, and general appearance.

Optical microscopic properties of asbestos and related minerals are given in Table 2. Your instructor will provide you with grain mounts of three Unknown asbestos minerals labeled Asbestos A, Asbestos B, and Asbestos C (the authors chose amosite, chrysotile and crocidolite) to examine under the petrographic microscope. The refractive index of the mounting medium will be in the standard range of 1.53-1.55. **Record as many of the optical microscopic properties of each sample as you are able to observe. (Your instructor may provide a form on which to record your observations.) If you are not using dispersion staining, give a name to each unknown based on the information in Table 2. Tell which property or properties were most useful for identifying each sample.**

Table 2. Optical Properties of Asbestos and Related Minerals

ACTIVITY 3 (OPTIONAL) - DISPERSION STAINING FOR IDENTIFYING ASBESTOS MINERALS

Dispersion staining is an optical identification technique that can be very helpful in identifying and distinguishing asbestos and non-asbestos fibers. The most diagnostic results are obtained when using a "central stop" objective (from McCrone Research Institute, see Information for Instructors) combined with a high-dispersion immersion oil (from Cargille Laboratories). The technique offers several advantages: 1) it is fast and easy and can be used successfully at the undergraduate level; 2) it yields highly diagnostic results that are unambiguous in their interpretation; and 3) it reinforces the concepts of light refraction and dispersion.

Most microscopists think of staining as applying a chemical dye that imparts a characteristic stain, or color, to plant or animal tissue. Dispersion staining is an optical phenomenon in which color is produced, not by a chemical interaction, but by the dispersion of the refractive index of a particle and the mounting liquid (McCrone, 1987). Light dispersion is what produces the colored Becke lines when the refractive indices of a crystal and liquid match. Because the refractive index of an anisotropic crystal will vary with crystal orientation, different dispersion colors will be obtained depending on the vibration direction of light. The dispersion staining technique enhances and clarifies the observed color lines by utilizing a high-dispersion immersion oil coupled with a special objective that blocks-out axial light and produces dark field illumination. For a less-expensive alternative, it is possible (although less satisfactory) to see dispersion colors by using oblique illumination (Bloss, 1961). The relation between crystallographic axes and highly elongated asbestos fibers allows for easy stage manipulation to test staining colors produced parallel and perpendicular to the vibration direction of light. The dispersion staining colors characteristic of each asbestos mineral are listed in Table 2. A flow chart outlining the procedure for identifying asbestos minerals with dispersion staining is shown in Figure 2.

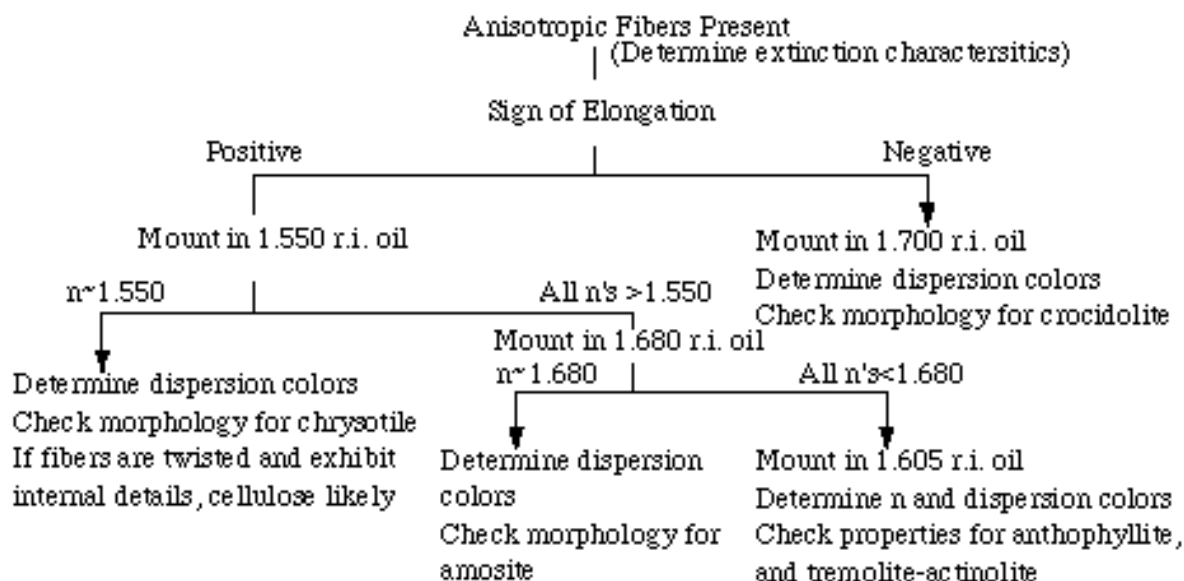


Figure 2. Flow chart outlining the procedure for identifying asbestos and related materials using dispersion staining. Samples should be examined first at low magnification in 1.550 r.i. oil. Non-fibrous materials and multiple fiber types may be present in bulk samples. If fibers are present, it must be determined whether they are isotropic or anisotropic. If fibers are isotropic, fiberglass (1-20 μm uniform diameter, r.i. < 1.53) or mineral wool (8-200 μm diameter, bulbous ends and shot, r.i. typically > 1.53) is indicated. For anisotropic fibers, view the fibers at 100X, and follow the flow chart.

Simple steps for dispersion staining:

- 1) Mount the fiber in a high-dispersion immersion oil that has a refractive index similar to that of the fiber.
- 2) Rotate the central-stop objective into the light path and close down the substage iris.
- 3) Rotate the microscope stage so that the elongate fiber lies parallel to the vibration direction of polarized light. Observe and record dispersion color (n_{\parallel}).
- 4) Rotate stage 90° so that elongate fiber lies perpendicular to the vibration direction of polarized light. Observe and record dispersion color (n_{\perp}).

The dispersion staining technique will be demonstrated to you. Use the technique to examine the asbestos unknowns and identify the minerals. If time and interest allow, you may be able to use this technique to analyze fibers from bulk samples of possible asbestos-containing material (ACM) that you have collected or that have been provided for you.

ACTIVITY 4 - ASBESTOS HAZARDS AND REGULATIONS (TURN IN AT YOUR NEXT LAB)

Asbestos has been used extensively for insulation of walls and pipes, as a binder in tiles, as the material of brake linings, for specialized textiles, for fire-proofing and to prevent corrosion on the hulls of ships. Occupational exposure to "blue asbestos" (crocidolite) has been shown to cause mesothelioma, a particularly nasty form of lung cancer, and its use has been banned almost worldwide (not specifically banned in U.S.). Occupational exposure (long-term exposure by mining or manipulating asbestos containing materials (ACM)) to other asbestos minerals is linked with asbestosis and lung cancer, especially in asbestos workers who also smoke. Occupational exposure to chrysotile (serpentine asbestos) is less likely to cause health problems than exposure to amphibole asbestos minerals (Ross, 1995; Mossman, et al., 1990; Skinner, et al., 1988).

Approximately 95% of the asbestos used in the United States is chrysotile. "Non-occupational exposure to chrysotile asbestos, despite its wide dissemination in urban environments throughout the world, has not been shown by epidemiological studies to be a significant health hazard" (Ross, 1984). For comparison, it is estimated that far more children die as a result of lightning strikes, drowning, and high school football accidents, to say nothing of automobile accidents and cigarette smoking, than might die as a result of asbestos exposure in schools. Asbestos removal from public and commercial buildings in the U.S. has cost from \$2 to 4 billion dollars per year in a few recent years. Removing the asbestos temporarily increases the fibers in the air and exposes a new generation of asbestos workers to occupational levels of exposure, and the asbestos containing material (ACM) has to be disposed of safely at great expense.

For your next lab, write a page stating why you believe that the U.S. government should or should not require the removal or repair of asbestos containing material (ACM) from public schools, under what conditions ACM should be removed and whether different asbestos minerals should be treated differently. You may refer to Table 3 and to the reading materials in the lab (see Reference list) to strengthen your arguments. You may also find useful information at these WWW addresses:

<http://www.asbestos-institute.ca/> The Asbestos Institute (a Canadian non-profit institute dedicated to promoting the safe use of asbestos)

http://www.osha-slc.gov/OshStd_data/1910.1001.html U.S. OSHA Asbestos Regulations

<http://www.abwam.com/grossing/refasbes.html> Asbestos Information from a Consulting Firm (Radon Detection Systems)

Table 3. Some Useful Facts about Asbestos and Asbestos Regulations

Asbestos-related Diseases (mainly from Ross, 1995)

Asbestosis- progressive lung fibrosis that causes shortness of breath and eventual death by lung or heart failure. It is caused by all types of asbestos, requires long exposure to high levels of airborne asbestos (occupational), and has a 10-20 year latency period.

Lung Cancer-the same type that is associated with cigarette smoking. It is caused by chrysotile, crocidolite and amosite, especially in those who smoke, requires long exposure to high levels of airborne asbestos (occupational) and has a 10-20 year

Mesothelioma-a cancer of the lining of the lung cavity, commonly results in death within 6-18 months of diagnosis. It is caused principally by exposure to crocidolite, to a lesser extent by amosite and has a very long latency period (>20 years). Low, non-occupational exposure to crocidolite can apparently cause mesothelioma.

with length:width ratio $\geq 3:1$, length greater than 5 μm and width less than 5 μm

(1972) 5 fibers/cm³

(1976) 2 fibers/cm³(1983) 0.5 fibers/cm³

(1986) 0.2 fibers/cm³

(1992) 0.1 fibers/cm³

0.00022 fibers/cm³ (Ross, 1995, from Health Effects Institute-Asbestos Report, 1991)

0.00039 fibers/cm³ (Mossman, et al., 1990)

er of schools in the U.S. estimated to have ACM

31,000 (Wilson, et al., 1994)

(from Mossman, et al., 1990)

(from Ross, 1995)

Nature of Risk	Risk of Death (per one million lifetimes)
Smoking (all causes)	210,000
Motor vehicle accidents	17,000
Home accidents	8,400
Falls	5,600
Drowning	2,100
Frequent airline passenger	1,000
Living in a brick building (radiation)	350
Electrocution	350
Tornadoes	49
Lightning	35
Hurricanes and tropical cyclones	28

ACKNOWLEDGMENTS

We thank John Brady and other members of the Organizing Committee for organizing the Teaching Mineralogy Workshop and the Workshop participants who took the role of students in this laboratory for their suggestions and lively discussion. LeeAnn Srogi, David Walker and Dexter Perkins are thanked for trying this laboratory in undergraduate classes and providing very helpful reviews.

REFERENCES CITED

- Bloss, F.D. (1961) An Introduction to the Methods of Optical Crystallography. Holt, Rinehart & Winston, New York, 294p.
- Deer, W.A., Howie, R.A., & Zussman, J. (1992) An Introduction to the Rock Forming Minerals. 2nd Edition, Longman, Essex, England, 696p.
- Gunter, M.E. (1994) Asbestos as a metaphor for teaching risk perception. *Journal of Geological Education*, 42, 17-24.
- Klein, C. (1995) Mineralogy Tutorials: Interactive Instruction on CD-ROM. John Wiley & Sons, Inc., New York.
- McCrone, W.C. (1987) Asbestos Identification. McCrone Research Institute, 2820 S. Michigan Avenue, Chicago, Illinois 60616-3292, 199p.
- Mossman, B.T., Bignon, J., Corn, M., Seaton, A., Gee, J.B.L. (1990) Asbestos: Scientific developments and implications for public policy. *Science* 247, 294-298.
- Ross, M. (1984) A survey of asbestos-related disease in trades and mining occupations and in factory and mining communities as a means of predicting health risks of nonoccupational exposure to fibrous minerals. In B. Levadie, Ed., ASTM Special Technical Publication 834, Definitions for Asbestos and other Health-related Silicates, 51-104 (out of print).
- Ross, M. (1995) The schoolroom asbestos abatement program: a public policy debacle. *Environmental Geology*, 26, 182-188.
- Skinner, H.C., Ross, M., and Frondel, C. (1988) Asbestos and other fibrous materials: mineralogy, crystal chemistry, and health effects. Oxford University Press, New York, 222 p.
- Veblen, D.R. & Wylie, A.G. (1993) Mineralogy of amphiboles and 1:1 layer silicates. In G.D. Guthrie, Jr. & B.T. Mossman, Eds., Health Effects of Mineral Dusts, Reviews in Mineralogy, 28, 61-137.

Wilson, R., Langer, A.M., Nolan, R.P., Gee, J.B.L., and Ross, M. (1994) Asbestos in New York City public school buildings--public policy: is there a scientific basis? *Regulatory Toxicology and Pharmacology*, 20, 161-169.

INFORMATION FOR INSTRUCTORS

Students in any particular mineralogy class will not necessarily know how to test all of the optical properties referred to in this laboratory exercise. Feel free to adapt the lab and encourage the students to apply any techniques they know how to use.

Source of Materials

Asbestos samples were purchased from Ward's Earth Science (Asbestos Standards Set, 49 E 5840, \$126 (includes Clinochrysotile, Thetford, Quebec; Chrysotile, Globe, Arizona; Actinolite, Chester, Vermont (cleavage fragments); Anthophyllite, Udiapur, India; Crocidolite, South Africa; Tremolite, Harquahala Mts., Arizona; Amosite, South Africa)). Grain mounts were made by H.L. from the samples described above (careful handling in a hood with paper face mask). The CD-ROM, Mineralogy Tutorials (ISBN 0-471-10996-7; current price \$395) was purchased from John Wiley & Sons. The central-stop objective (part # 289F; cost approximately \$500) and information about the dispersion staining technique were obtained by S.H. from McCrone Research Institute, 2820 S. Michigan Avenue, Chicago, Illinois 60616-3292, phone 800-622-8122 (URL <http://www.mccrone.com>). High-dispersion oils (approximately \$60 per bottle) can be obtained from R.J. Cargille Laboratories Inc., phone 201-239-6633.

Handling Asbestos

Hand specimens for this laboratory are sealed in zip-lock plastic bags (double bagging for crocidolite and amosite). Grain mounts are permanently sealed in CR-1 Cover Glass Mounting Medium (Wards 37 E 9550) with a refractive index of 1.535. Direct handling (e.g., preparation of microscope mounts) of amphibole asbestos and bulk samples that may contain crocidolite or amosite asbestos should probably be done in a hood. Limited handling of chrysotile is not believed by most mineralogists to be hazardous to students or instructors.